



Keywords: WLP, SMT, PCB design, wafer level package, tape and reel, T&R

APPLICATION NOTE 1891

WAFER-LEVEL PACKAGING (WLP) AND ITS APPLICATIONS

Abstract: This application note discusses Maxim Integrated's wafer-level package (WLP) and provides the PCB design and SMT assembly guidelines for the WLP.



[Click here for an overview of the wireless components used in a typical radio transceiver.](#)

Introduction

The wafer-level package (WLP) offers advantages of small size and low inductance. Maxim Integrated's WLP are manufactured on wafers. Backside lamination is applied to enhance the mechanical strength of WLP body. Pb-free solder balls are used as die to PCB interconnects. An example package outline is showing in **Figure 1**.

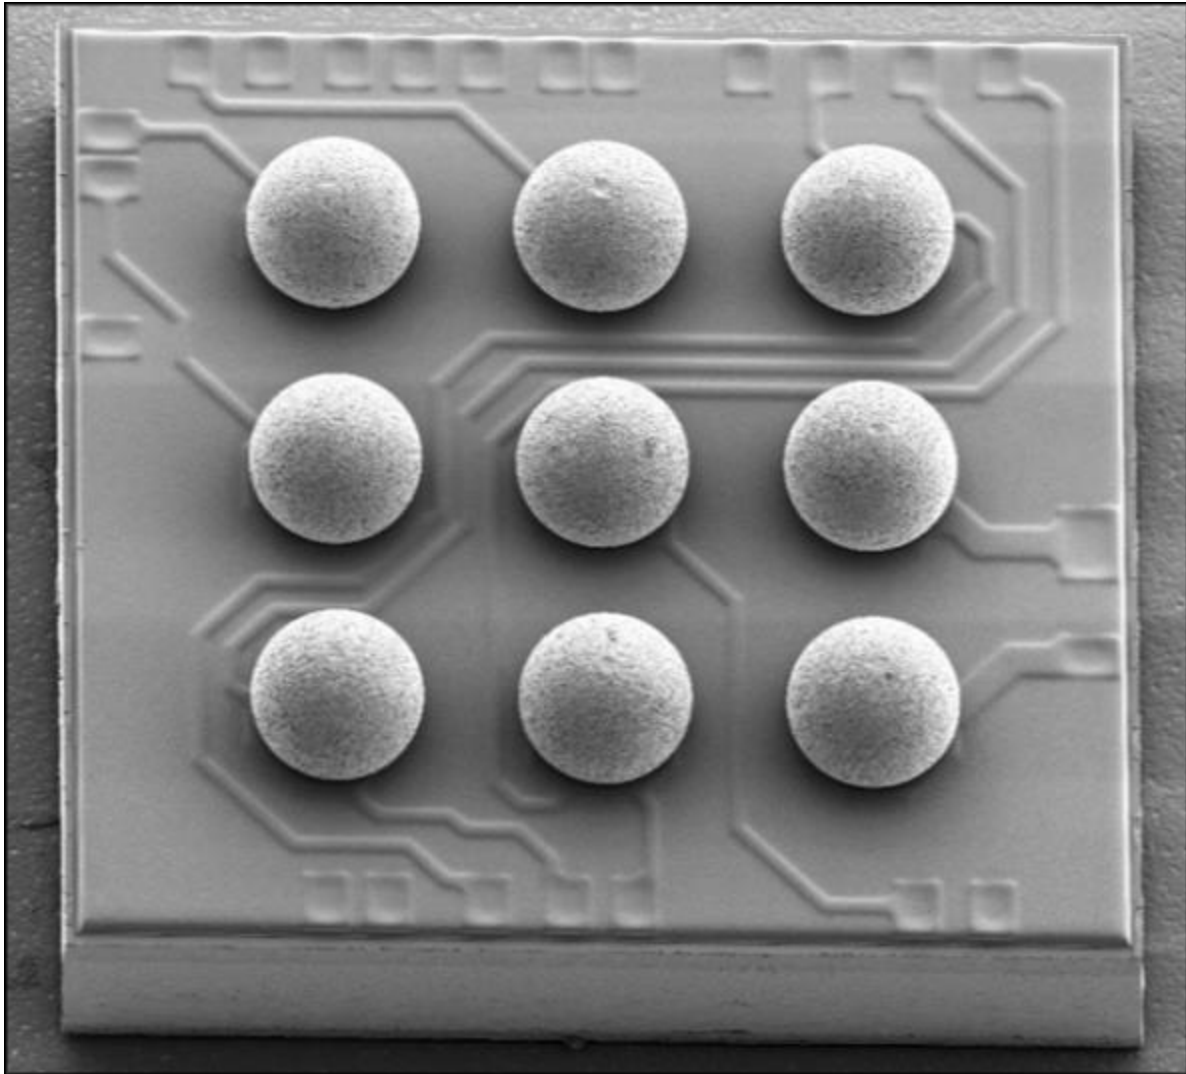


Figure 1. SEM photo of a WLP.

Maxim Integrated ships WLPs in tape-and-reel (T&R) format. Tape-and-reel requirements are based on the EIA-481 standard.

[Additional T&R information ›](#)

Figure 2. Package outline drawing of a 0.4mm pitch WLP.

PCB Design

Two types of land patterns are used for surface-mount packages (**Figure 3**):

- NSMD (nonsolder mask defined) pads—the soldermask opening is larger than the metal pads. The NSMD pad size is the same as the metal pad.
- SMD (soldermask defined) pads—the soldermask opening is smaller than the metal pad. The SMD pad size refers to the size of soldermask opening.

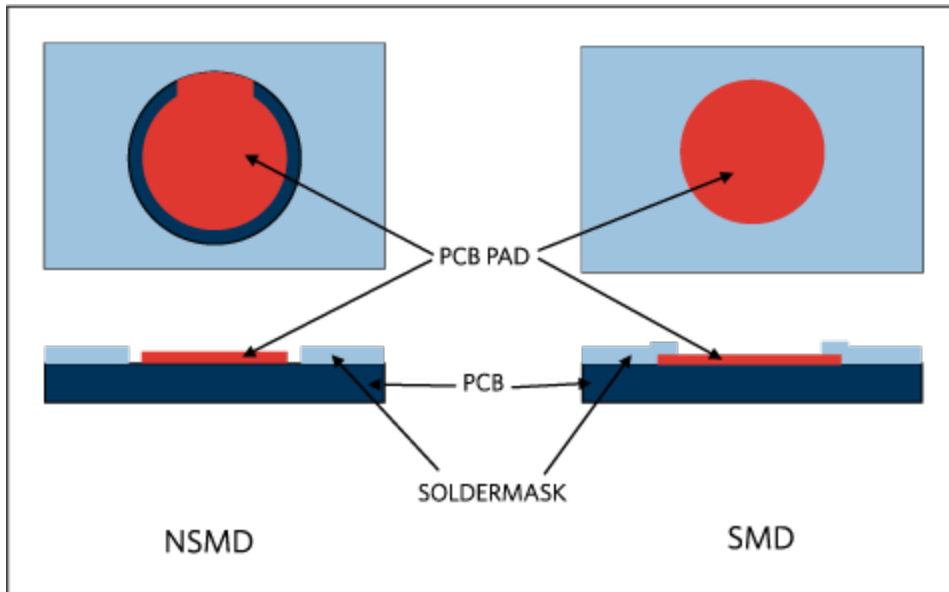


Figure 3. Illustration of NSMD and SMD land pad patterns.

Although both NSMD and SMD pads are used in applications, NSMD pads are recommended. NSMD pads have the advantages of more precise pad dimension and better solder joint reliability at board side. Only one type of a pad (NSMD or SMD) and one type of pad surface finish should be used at a given footprint. The recommended pad sizes are listed in **Table 1**. The width of the trace at entry to an NSMD pad should be no more than 100 μ m to avoid excessive wetting of solder onto the trace, which can change the solder joint shape. A teardrop is recommended at the trace entry to lower the risk of trace crack.

When wide trace entry to a pad is required for reasons such as high current carrying, SMD pads can be used. Larger metal pads and wider metal traces can be used for SMD pads.

Via in pad (VIP) is acceptable. The dimple at VIP can cause solder voiding at assembly. Small voids at VIP do not significantly degrade the solder joint reliability. The user is suggested to assess the acceptable via quality. Complete flat VIP can be achieved with via capping although it is not required. It is recommended to put VIP at corner ball location to improve the PCB reliability.

Table 1. Recommended NSMD Pad Designs


Ball Pitch(mm)	Acceptable PCB Pad Diameter (μ m)	Recommended PCB Pad Diameter (μ m)
0.5	220 to 280	250
0.4	200 to 260	250
0.35	190 to 220	200
0.3	160 to 190	180

PCB Surface Finish

OSP (Organic Solderability Preservative), ENIG (Electroless Nickel/Immersion Gold), Electrolytic Nickel/Gold, ENEPIG (Electroless Nickel Electroless Palladium/Immersion Gold), Immersion Silver and Immersion Tin finishes are used in the industry. OSP is recommended for applications that require drop test reliability.

SMT Assembly

Standard SMT equipment and process are used for WLP assembly. The process flow is the following:

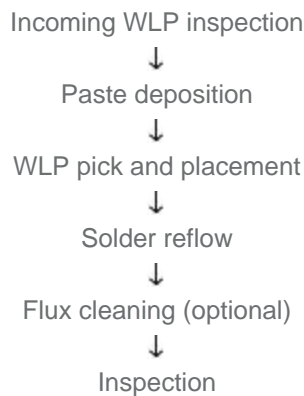

Both solder paste or flux printing and flux dipping approaches provide acceptable assembly quality and reliability. Maxim Integrated WLP meet JEDEC level 1 moisture sensitivity classification. No baking is needed before assembly.

Stencil Design

Solder paste, paste flux, or liquid flux can be printed to the PCB with a stencil prior to the assembly. High-quality laser-cut stainless steel stencil with nano coating improves transfer efficiency and consistency. It is recommended for WLPs, especially those with pitch smaller than 0.4mm. SPI (solder paste inspection) is also recommended for such fine-pitch WLP assembly. The optimum stencil aperture size depends on stencil manufacturing technology, printing equipment, solder paste type, and process parameters. Recommended stencil thickness and reference aperture sizes are listed in **Table 2**.

Table 2. Stencil Thickness and Aperture

WLP Ball Pitch	0.5mm Pitch	0.4mm Pitch	0.35mm Pitch
Recommended stencil thickness	4 mils	4 mils	4 mils
Reference stencil aperture size	250µm	250µm	200µm

Paste printing for 0.3mm pitch WLP is challenging. Users should determine stencil design based on the equipment capability, solder paste choice, and stencil technology. Alternatively, flux dipping is can be used.

Solder Paste

Conventional Pb-free solder pastes can be used for WLP assembly. Type 3 pastes can be used for 0.5mm and 0.4mm pitch WLP assembly while a type 4 paste is preferred for 0.35mm and 0.3mm pitch WLP. SnPb solder paste should not be used for Pb-free WLP assembly.

Automated Component Pick and Place

Standard pick and place equipment can be used for placing Maxim Integrated WLP. A fine pitch IC packaging placement equipment is preferred for better accuracy. Plastic pick up nozzles are recommended. Pick and place force should not exceed 2N.

WLP body outline can be used for component recognition. For better placement accuracy, solder balls can be used for alignment. With this approach, a look-up camera is used to recognize the solder balls. The equipment enters the ball array itself to the footprint for better alignment accuracy.

Reflow

All Maxim Integrated WLPs are compatible with industry-standard solder reflow processes. An optimized reflow profile takes into account of flux type and all components to be soldered to the board. Use of nitrogen inert-atmosphere reflow is optional. It has demonstrated a better centering of the Pb-free WLP on the pads and less solder oxidation compared to air reflow.

Flux Cleaning

Post reflow cleaning is not recommended especially when a no-clean type solder paste is used. If cleaning is required, a spray-under-immersion or ultrasonic-immersion cleaning method is recommended. A thorough study of flux, paste, and cleaning solvent compatibility must be evaluated.

Underfill

In general, underfill material is not required for WLP. In certain applications, underfill can enhance WLP mechanical robustness when proper underfill material is selected.

Rework

Rework is not recommended. It should only be performed using a controlled and qualified process that prevents mechanical and ESD damage.

Reliability

Reliability requirements are listed in **Table 3**.

Table 3. Reliability Qualification Requirements

Stress	Specification	Abbv	Condition	No. of Lots/SS per Lot	Duration/Acceptance
MSL Preconditioning	JESTD20	PC	MSL1	3 lots/150 units	Visual and Electrical test
High Temperature Storage	JESD22-A103	HTS	150°C	3 lots/77 units	1000hrs/0 Fail
Temperature Cycling	JESD22-A104	TC	-40°C to +125°C 1 cycle/hr	3 lots/77 units	1000 cycles for array size 6x6/note 500 cycles for array size > 6x6/note
Operating Life Test	JESD22 A108	HTOL	T _J = 135°C	3 lots/77 units	1000hrs/0 Fail
Drop Test	JESD22-B111	DT	Cond B	1 lot/60 units	150 drops/note

Note: Meet less than 5% failure rate at 90% confidence level at the number of cycles specified for the reliability stress.

Thermal Performance

Thermal modeling is performed with JEDEC still air conditions. The junction-to-ambient thermal resistance values for 0.5mm and 0.4mm pitch WLP are listed in **Table 4** and **Table 5**, respectively.

Table 4. Thermal Resistance of 0.5mm pitch WLP

Array Size	Pitch (mm)	θ_{JA} (°C/W) for 1S0P Board	θ_{JA} (°C/W) for 2S2P Board
2x2	0.5	329.2	87.4
4x4	0.5	154.8	49.1
6x6	0.5	110.4	37.7
8x8	0.5	87.8	31.6
10x10	0.5	73.4	27.7
12x12	0.5	63.4	24.8
14x14	0.5	55.9	22.5

Table 5. Thermal Resistance of 0.4mm pitch WLP

Array Size	Pitch (mm)	θ_{JA} (°C/W) for 1S0P Board	θ_{JA} (°C/W) for 2S2P Board
2x2	0.4	434.5	102.6
4x4	0.4	209.7	57.9
6x6	0.4	151.3	45.7
8x8	0.4	121.2	38.2
10x10	0.4	101.9	33.6
12x12	0.4	88.4	30.2
14x14	0.4	78.1	27.5

More Information

For Technical Support: <http://www.maximintegrated.com/en/support>

For Samples: <http://www.maximintegrated.com/en/samples>

Other Questions and Comments: <http://www.maximintegrated.com/en/contact>

Application Note 1891: <http://www.maximintegrated.com/en/an1891>

APPLICATION NOTE 1891, AN1891, AN 1891, APP1891, Appnote1891, Appnote 1891

© 2014 Maxim Integrated Products, Inc.

The content on this webpage is protected by copyright laws of the United States and of foreign countries.

For requests to copy this content, [contact us](#).

Additional Legal Notices: <http://www.maximintegrated.com/en/legal>